

X-Ray Absorption Spectroscopic Study of the Transition-Metal-Only Double Perovskite Oxide $\text{Mn}_2\text{CoReO}_6$

Xiao Wang,^{1,*} Jie Zhang,^{1,2} Zhao Pan,¹ Dabiao Lu,^{1,2} Maocai Pi,^{1,2} Xubin Ye,¹ Cheng Dong,¹ Jie Chen,³ Kai Chen,⁴ Florin Radu,⁵ Sonia Francoual,⁶ Stefano Agrestini,⁷ Zhiwei Hu,⁸ Chun-Fu Chang,⁸ Arata Tanaka,⁹ Kazunari Yamaura,^{10,11} Yao Shen,^{1,2,**} and Youwen Long^{1,2,12,***}

¹Beijing National Laboratory for Condensed Matter Physics, Institute of Physics, Chinese Academy of Sciences, Beijing 100190, China

²School of Physical Sciences, University of Chinese Academy of Sciences, Beijing 100049, China

³Laboratory for Materials and Structures, Institute of Innovative Research, Tokyo Institute of Technology, Yokohama, Kanagawa 226–8503, Japan

⁴National Synchrotron Radiation Laboratory, University of Science and Technology of China, Hefei 230026, China

⁵Helmholtz-Zentrum Berlin für Materialien und Energie, Albert-Einstein-Str.15, 12489 Berlin, Germany

⁶Deutsches Elektronen-Synchrotron (DESY), Notkestraße 85, 22607 Hamburg, Germany

⁷Diamond Light Source, Didcot, United Kingdom

⁸Max Planck Institute for Chemical Physics of Solids, Nöthnitzer Straße 40, 01187 Dresden, Germany

⁹Quantum Matter Program, Graduate School of Advanced Science and Engineering, Hiroshima University, Higashi-hiroshima 739-8530, Japan.

¹⁰Research Center for Materials Nanoarchitectonics (MANA), National Institute for Materials Science, Namiki 1-1, Tsukuba, Ibaraki, 305-0044, Japan

¹¹Graduate School of Chemical Sciences and Engineering, Hokkaido University, North 10 West 8, Kita-ku, Sapporo, Hokkaido, 060-0810, Japan

¹²Songshan Lake Materials Laboratory, Dongguan, Guangdong 523808, China

*wangxiao@iphy.ac.cn

**yshen@iphy.ac.cn

***ywlong@iphy.ac.cn

Abstract

By means of x-ray absorption spectroscopic studies, both experimentally and theoretically, we investigated the magnetic properties of the transition-metal-only double perovskite oxide $\text{Mn}_2\text{CoReO}_6$, which experiences an antiferromagnetic transition at $T_N = 93$ K whereas holds a considerable net moment at low temperature. Internal magnetic fields against the applied magnetic field for all the transition metal ions were identified, providing a microscopic insight of the intra-site antiferromagnetic couplings. Nevertheless, parallelly oriented canted spins of the Mn, Co and Re cations were observed. In particular, the Mn and Co cations hold considerable canting moments, which can be ascribed to the competition between the ferromagnetic inter-site and antiferromagnetic intra-site magnetic interactions. Moreover, a linear magnetoresistance effect was observed below T_N . The concurrence of the magnetoresistance effect and the antiferromagnetic nature make $\text{Mn}_2\text{CoReO}_6$ a promising candidate for high-speed and energy-saving spintronics applications.

Introduction

The realization and utilization of both charge and spin degrees of freedom of the electrons underpins spintronics.^{1–3} Reported spin-dependent electron transport mechanisms are giant magnetoresistance (GMR) in trilayer heterostructures with a nonmagnetic spacer sandwiched by two ferromagnetic (FM) electrodes,⁴ tunnel magnetoresistance (TMR)⁵ in magnetic tunnel junctions (MTJs), and magnetic random access memories (MRAMs).⁶

Antiferromagnetic (AFM) spintronics has attracted intense attention owing to its fast dynamics with frequency up to terahertz.⁷ However, the zero net moment of the AFM materials severely impedes the manipulation of the magnetization, leaving great challenges in applications. Nevertheless, multiple spin dependent phenomena have been discovered in AFM materials that can encode and transport information through such as magnetoresistance (MR),⁸ magnetoelectric multiferroics,⁹ anomalous Hall effect,¹⁰ spin torque,¹¹ magneto-optical Kerr effect,¹² *etc.* Therefore, AFM materials hold great opportunities for both academic studies and functional applications.

Double perovskite oxides with a formula of $\text{A}_2\text{BB}'\text{O}_6$ can flexibly accommodate different types of ions at the A, B and B' sites, making them attractive for engineering and studying potentially new spintronic materials. For example, the up-spin channel of $\text{Sr}_2\text{FeMoO}_6$ opens up a gap while the down-spin channel is conductive, making it a half metal with 100% spin polarization

and exhibiting GMR.^{13,14} Similar half metallic behavior combined with GMR is also observed in double perovskite $\text{Sr}_2\text{FeReO}_6$.¹⁵ $\text{Sr}_2\text{CrOsO}_6$ has a super high T_C of 725 K as a result of the robust AFM coupling between the Cr and Os ions at the B and B' sites, respectively.¹⁶ Y_2NiIrO_6 exhibits giant exchange bias attributable to the pinned magnetic domains due to the combination of strong spin-orbit coupling of the Ir ions and the AFM coupling of the Ni and Ir sublattices.¹⁷ In most cases, the A site of double perovskites host nonmagnetic ions such as alkali, alkali earth and lanthanides. Recent studies have shown that transition metals can also occupy the A site, resulting in novel magnetic and electronic interactions through the A-B and A-B' pathways, further leading to intriguing properties for the transition-metal-only double perovskite oxides such as half metallicity,¹⁸ GMR,¹⁹ cation rattling,²⁰ and multiferroicity.²¹

Nevertheless, the studies on transition-metal-only double perovskite oxides are still limited. The small transition metal at the A site leads to a significant mismatch between the A and B sites, resulting in significant tilt of the BO_6 octahedra. To the best of our knowledge, the few reported transition-metal-only double perovskites are prepared under high pressure over 5 GPa.^{18–23} $\text{Mn}_2\text{CoReO}_6$ (MCRO) is the fourth known transition-metal-only double perovskite oxides.²³ It experiences an antiferromagnetic transition at $T_N = 93$ K nevertheless possesses a considerable net moment at low temperature. In this paper, by experimental and theoretic x-ray absorption spectroscopic studies, together with multiple measurements, we obtained a negative internal magnetic field for all the three transition metal cations, indicating the dominant AFM intra-site magnetic couplings. However, parallel canting spins of Mn, Co and Re are identified. In particular, the Mn and Co cations hold considerable canting moments, which can be ascribed to the competition between the intra- and inter-sites magnetic interactions between them. On the other hand, a linear MR effect was observed below T_N . Therefore, MCRO holds basic traits that are relevant to future high-speed and energy-saving AFM spintronics applications.

Methods

Polycrystalline MCRO was synthesized under high-pressure and high-temperature (HPHT) conditions. Stoichiometric high purity (> 99.9%) starting materials MnO , CoO and ReO_3 were thoroughly ground with an agate mortar in argon gas atmosphere. Then the mixed powder was pressed into a platinum capsule of 3 mm diameter and 4 mm height and then treated with an anvil-type high-pressure apparatus under 9 GPa and 1523 K for 30 minutes. After the HPHT treatment

the temperature was quenched to room temperature in seconds and the pressure was slowly released to ambient in several hours.

The synchrotron x-ray diffraction (SXR) patterns were collected at the BL02B2 ($\lambda = 0.65$ Å) beam line of SPring-8 in Hyogo. The 2θ scan was performed from 2° to 70° with a step of 0.006° . The Rietveld refinement of crystallographic parameters was performed using the GSAS software package.²⁴ The magnetic susceptibility and magnetization were measured using a Quantum Design superconducting quantum interference device magnetometer (MPMS-3). Both zero-field-cooling (ZFC) and field-cooling (FC) modes were adopted for magnetic susceptibility measurements with a 0.1 T magnetic field. The resistivity was measured using a sample pellet with the size of about $2 \times 1 \times 1$ mm³ by a standard four-probe method on a Quantum Design physical property measurement system (PPMS-7). The heat capacity was measured using a sample pellet of size about $2 \times 2 \times 0.4$ mm³ on PPMS-7.

The Mn- $L_{2,3}$ and Co- $L_{2,3}$ x-ray absorption spectroscopy (XAS) were measured at room temperature via total electron yield (TEY) mode at TPS 45A beamline of National Synchrotron Radiation Research Center (NSRRC) in Hsinchu. The Mn- $L_{2,3}$ and Co- $L_{2,3}$ x-ray magnetic circular dichroism (XMCD) were measured at 10 K and 8 T using TEY mode at the VEKMAG end station²⁵ at the HZB/BESSY II synchrotron radiation facility in Berlin. The XAS and XMCD at the Re- $L_{2,3}$ edges were measured in transmission at beamline P09 at PETRA III at DESY in Hamburg, and the Re- $L_{2,3}$ XMCD was measured at 10 K and 5 T. For the XMCD measurements, both the magnetic field and the polarization ($\sim 77\%$ for VEKMAG and $\sim 99\%$ for P09) of the light were flipped to obtain the μ^+ (parallel) and μ^- (antiparallel) spectra.

Results & Discussion

Figure 1 displays the SXR pattern of MCRO, which can be refined with the space group $P2_1/n$ (No. 14) with lattice parameters $a = 5.23506(1)$ Å, $b = 5.35179(1)$ Å, $c = 7.63109(2)$ Å, and $\beta = 89.966(0)^\circ$. The crystal structure was depicted in the inset at the right side of Figure 1. As shown in Figure 1 and the inset in the middle, the (011) diffraction peak clearly indicates the rocksalt-type distribution of Co and Re at the B and B' sites, respectively.²⁶ A slight anti-site occupancy of 2% between the Co and Re was found. A previous neutron powder diffraction (NPD) also indicated $\sim 16\%$ disorder between A-site Mn and B-site Co.²³ The detailed refined parameters from SXR are listed in Table S1. The valence states of Mn²⁺ and Co²⁺ can be obtained via the bond valence

sum (BVS)²⁷ calculations based on the refined bond lengths (Table S2). For Re, the averaged Re-O bond length is 1.920 Å, very close to that of Sr₂MgRe⁶⁺O₆ (1.912 Å),²⁸ indicating a Re⁶⁺ state for MCRO.

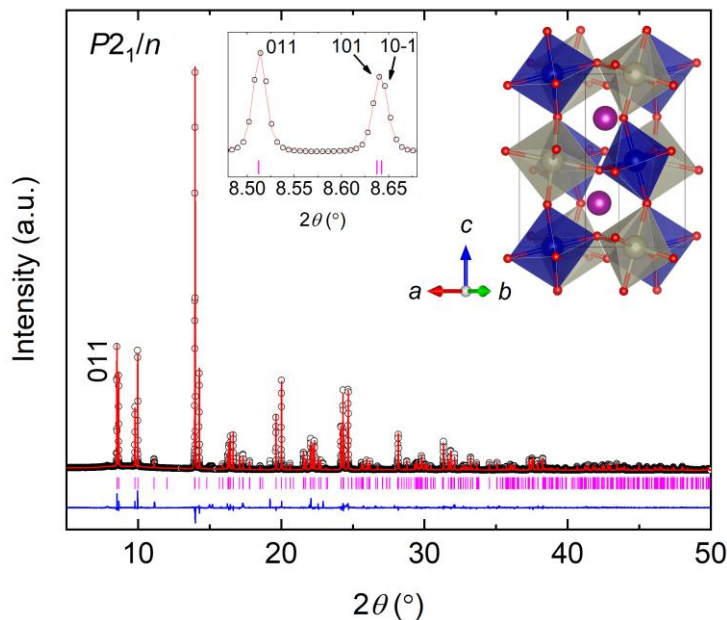


Figure 1. SXRD pattern and Rietveld refinement of MCRO. The black circles, red lines and blue lines indicate the observed, calculated and difference, respectively. The magenta ticks indicate the allowed Bragg reflections for space group $P2_1/n$. The inset in the middle displays the SXRD pattern near the (011) diffraction peaks. The inset at the right side displays the crystal structure of MCRO. Mn, Co, Re and O are shown in purple, blue, grey and red, respectively.

In order to directly obtain the valence states of the cations in MCRO, we performed XAS measurements. It is well known that the XAS is an element selective technique highly sensitive to the valence state. For an open d shell system, an increase of the valence of the transition metal ion by one leads to a shift of the $L_{2,3}$ XAS spectrum to higher energies by one electron volt (eV) or more that is also accompanied by remarkable changes of the spectral feature.^{29–31} As shown in Figure 2a, the white line of the Mn- $L_{2,3}$ XAS of MCRO resembles that of Mn²⁺ reference compound MnO with the L_2/L_3 peak locating at the same energy as that of MnO, which points to the occurrence of a Mn²⁺ valence state. Similarly, as shown in Figures 2b and 2c, the peak energies and the shape of the white lines of the Co- $L_{2,3}$ and Re- L_3 XAS respectively resemble that of the high-spin Co²⁺ and Re⁶⁺ references,³² indicating the occurrence of high spin Co²⁺ ($t_{2g}^5 e_g^2$) and Re⁶⁺ valence states. Therefore, the valence configuration Mn²⁺/Co²⁺/Re⁶⁺ is experimentally validated.

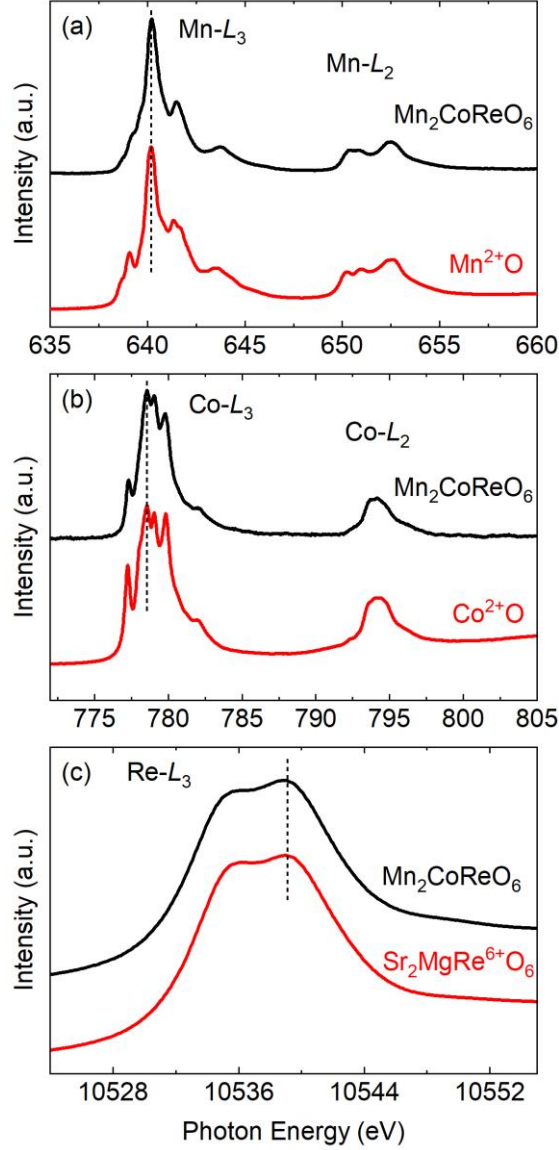


Figure 2. XAS at the (a) Mn- $L_{2,3}$, (b) Co- $L_{2,3}$, and (c) Re- L_3 edges of MCRO. The XAS of MnO, CoO and $\text{Sr}_2\text{MgReO}_6$ are displayed as Mn^{2+} , Co^{2+} and Re^{6+} references, respectively.

After the determination of the structure and the valence states, we continue with the description of the magnetic properties of MCRO. Figure 3a displays the temperature-dependent magnetic susceptibility of MCRO. At $T_N = 93$ K, an AFM transition can be clearly identified. An NPD study has demonstrated that this AFM transition is related to the antiparallel spin alignment of all of the Mn, Co, and Re sublattices.²³ It is worth noting that the AFM transition is relatively broad in temperature, as an implication of competing FM and AFM coupling mechanisms. Moreover, the ZFC and FC curves start to separate below T_N (see inset of Figure 3a) and further

split with temperature decreasing, indicating the formation of a canted AFM structure. As shown in Figure 3b, the Curie-Weiss fitting was performed above 180 K with the function $\chi^{-1} = (T - \theta)/C$. The positive Weiss temperature $\theta = 50$ K indicates the presence of FM interactions in $\text{Mn}_2\text{CoReO}_6$. According to the fitted Curie constant, $C = 8.18 \text{ emu K mol}^{-1} \text{ Oe}^{-1}$, the effective magnetic moment is calculated to be $\mu_{\text{exp}} = 8.09 (\sqrt{8C})$ Bohr magnetons per formula unit ($\mu_{\text{B}}/\text{f.u.}$), slightly smaller than the spin-only theoretical value of $9.38 \mu_{\text{B}}/\text{f.u.}$ ($g\sqrt{\sum_i S_i(S_i + 1)}$, where $g = 2$ is the Landé factor of spins), considering Mn^{2+} ($S = 5/2$), Co^{2+} ($S = 3/2$, high-spin), and Re^{6+} ($S = 1/2$) ions. The smaller experimental value can be a result of a reduction of Re^{6+} moment through the spin-orbit coupling. Figure 3c displays the isothermal field-dependent magnetization of MCRO. At temperatures above T_{N} , the magnetization is linearly dependent on the magnetic field, in agreement with a paramagnetic state. When temperature further decreases down to 2 K, a prominent hysteresis and a moment of $1.1 \mu_{\text{B}}/\text{f.u.}$ at 7 T can be found, which is indicative of the competition between the AFM and FM couplings which will be discussed later.

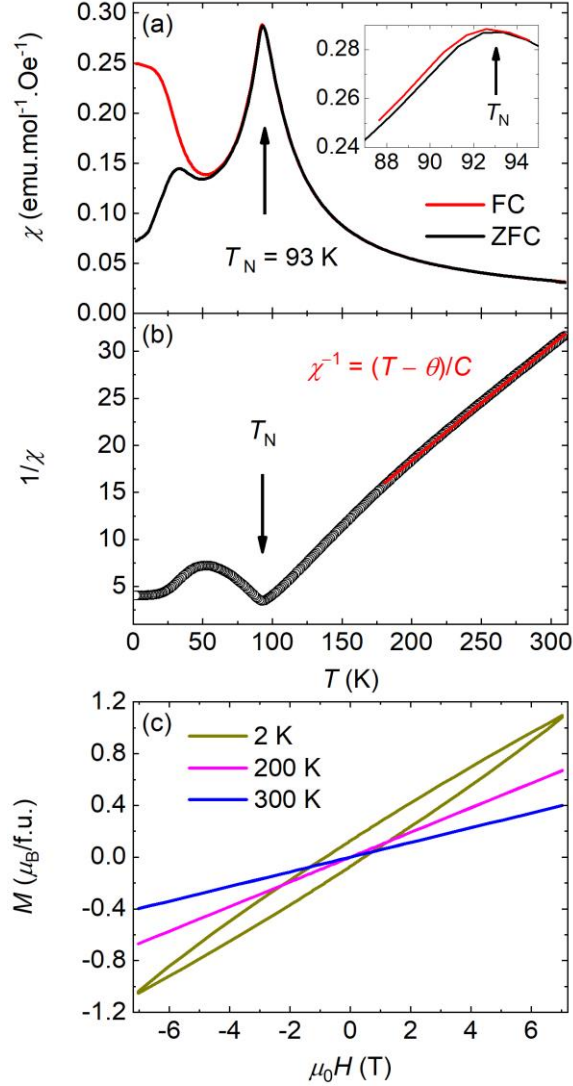


Figure 3. (a) Temperature dependent magnetic susceptibility of MCRO. The inset displays the region near $T_N = 93$ K. (b) The inversed magnetic susceptibility (black circles) and the Curie-Weiss fitting above 180 K with formula $\chi^{-1} = (T - \theta)/C$. (c) Field dependent magnetization of MCRO at selected temperatures.

We further measured the heat capacity of MCRO. As shown in Figure 4a, a cusp feature emerges at T_N , in agreement with the AFM transition. It is worth noting that this feature is relatively weak, quite different from the sharp peak expected at AFM transitions.³³ In order to display the ingredients that contribute to the heat capacity, we plotted the $C_P/T-T^2$ plot below 10 K, as depicted in Figure 4b. The convex curve at low temperature clearly indicates the magnetic contribution on the specific heat, in accord with the concurrence of both magnetic and antiferromagnet interactions

in MCRO. The heat capacity can be well fitted with formula $C_P/T = \alpha T^2 + \beta T^{1/2} + \gamma$, with $\alpha = 1.53 \text{ mJ mol}^{-1} \text{ K}^{-4}$, $\beta = 23.5 \text{ mJ mol}^{-1} \text{ K}^{-5/2}$, and $\gamma = 4.24 \text{ mJ mol}^{-1} \text{ K}^{-2}$, indicating that the phonons, magnons and electrons all contribute to the heat capacity, in agreement with the canted AFM semiconductive nature of MCRO.

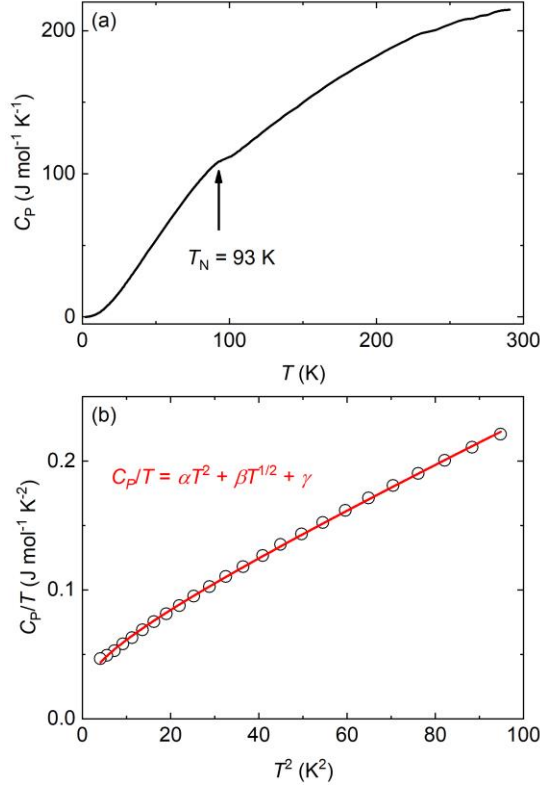


Figure 4. (a) Temperature dependent heat capacity of MCRO. (b) Experimental heat capacity below 10 K (black circles) and the fitting with formula $C_P/T = \alpha T^2 + \beta T^{1/2} + \gamma$ (red line).

In order to obtain a deeper insight of the configuration of the canted spins, we performed XMCD measurements on the Mn, Co and Re ions. It is known that the element-selective XMCD is a sensitive probe for determining the spin alignment of the magnetic ions.^{32,34,35} As shown in Figure 5, the XMCD signal at the L_3 (L_2) edge of all transition metals is negative (positive), demonstrating that the resultant spins direction of Mn, Co and Re are parallel to each other in an applied magnetic field.^{36,37} Herein, MCRO provides a very rare example in double perovskite with parallel spins at all A, B, and B' sites. Usually, the superexchange coupling between the $5d$ and $3d$ ions through the A/B-O-B' pathway as well as a two sublattice double-exchange mechanism³⁸ can lead to the magnetic property. For example, in $\text{Sr}_2\text{FeReO}_6$, $\text{Sr}_2\text{CrOsO}_6$ and Y_2NiIrO_6 , the B-site $3d$

and B'-site $5d$ ions are ferrimagnetically (FiM) coupled.^{15–17} Similar FiM structures can be also found in the quadruple perovskite oxides $\text{CaCu}_3\text{Fe}_2\text{B}'_2\text{O}_{12}$ ($\text{B}' = \text{Re}$ and Os).^{39–41}

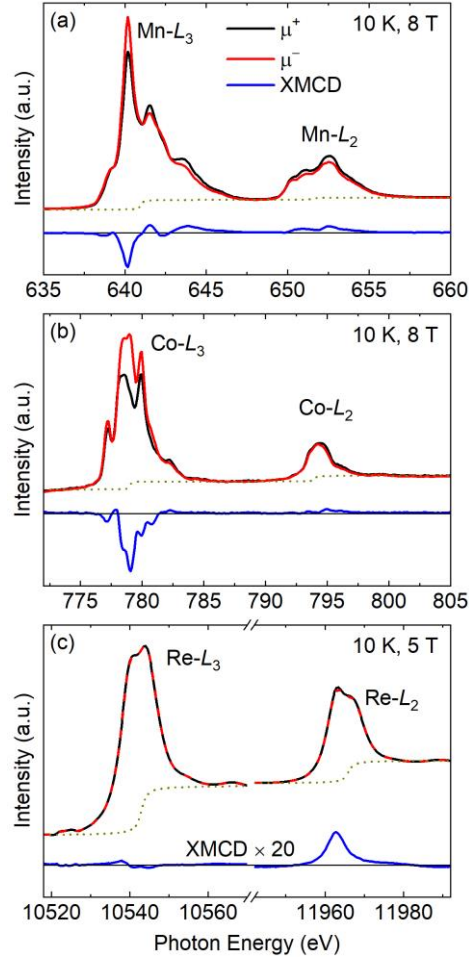


Figure 5. XMCD spectra at the (a) Mn- $L_{2,3}$, (b) Co- $L_{2,3}$, and (c) Re- $L_{2,3}$ edges of MCRO. The XAS with light polarization parallel (μ^+ , black lines) and antiparallel (μ^- , red lines) to the magnetic field are shown. The blue lines are the XMCD ($\mu^+ - \mu^-$) spectra. The dashed lines indicate the edge jump.

One can observe that the XMCD signal for all the three cations Mn, Co and Re are much smaller than the typical ferromagnets,^{42,43} as the net magnetization is from canted spins. In order to obtain an inner view of the magnetic moments of the cations, we performed full-atomic-multiplet ligand-field calculations using the XTLS code.⁴⁴ This theoretic calculation includes the full intra-atomic multiplet interactions, the atomic d spin-orbit coupling (SOC), the transition metal d to O- $2p$ hybridization, and the crystal field interaction. This model has very successfully

reproduced the line shape of XMCD spectra of transition metal element in the past decades.^{45,46} The parameters are listed in Ref. 47. The calculations well reproduce the measured spectra, as shown in Figure 6. In our calculations, in order to obtain the intensity of the XMCD signal, negative exchange fields (H_{ex}) were adopted for all the three transition metal ions Mn^{2+} , Co^{2+} and Re^{6+} .⁴⁷ The negative H_{ex} is indicative of an internal magnetic field against with the applied field. These results provide a microscopic insight of the intra-site AFM couplings of the Mn, Co and Re sublattices.

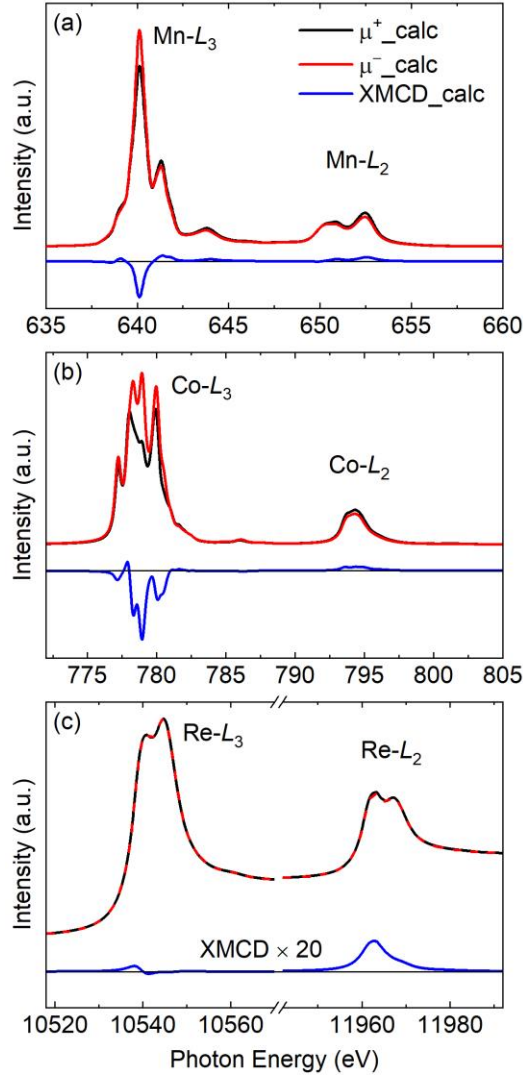


Figure 6. Calculated XMCD spectra at the (a) Mn- $L_{2,3}$, (b) Co- $L_{2,3}$, and (c) Re- $L_{2,3}$ edges of MCRO. The XAS with light polarization parallel (μ^+ , black lines) and antiparallel (μ^- , red lines) to the magnetic field are shown. The blue lines are the XMCD ($\mu^+ - \mu^-$) spectra.

From the cluster calculation, the spin and orbital moments of Mn, Co and Re are listed in Table 1. A total moment of $1.83 \mu_B/\text{f.u.}$ is obtained. The larger moment than the magnetization measurements (Figure 3c) could be a result of the stronger applied magnetic field for the XMCD measurements. One can also find considerable spin moments of Mn and Co, indicating that the spins of Mn and Co are notably canted along the applied magnetic field. Note that the orbital moment of Mn^{2+} is negligible because of the half-filled $3d$ orbit ($t_{2g}^3 \uparrow e_g^2 \uparrow$). On the contrary, the spin moment of Re is very small, indicating that the AFM alignment of the Re spins almost maintain.

Table 1. Spin and orbital moments from calculations.

	M_{spin}	M_{orb}
Mn (μ_B/atom)	0.471	/
Co (μ_B/atom)	0.638	0.251
Re (μ_B/atom)	0.0159	-0.0144
Total ($\mu_B/\text{f.u.}$)	$1.83 \mu_B/\text{f.u.}$	

In order to understand the different canting behavior between Mn/Co and Re sites, we discuss the possible magnetic interactions in MCRO. The intra-site AFM structure is indicative of the dominate long-range superexchange pathway M-O-M'-O-M, as a consequence of the energy differences of the orbitals between the M and M' ions.^{48,49} Here in MCRO, different orbitals of $3d$ - e_g , $3d$ - t_{2g} and $5d$ - t_{2g} for Mn^{2+} ($3d^5$), Co^{2+} ($3d^7$) and Re^{6+} ($5d^1$), respectively, are involved in the magnetic couplings, giving rise of the domination of the long-range superexchange couplings. On the other hand, the canted moments of MCRO indicate the competition of magnetic interactions against the long-range superexchange one. Here we consider the superexchange pathway M-O-M'. As shown in Figure 7 and Table S3, the bond angle(s) $\angle\text{Mn-O-Co}$ and $\angle\text{Mn-O-Re}$ are close to 90° , and $\angle\text{Co-O-Re}$ is close to 180° . According to the Goodenough-Kanamori-Anderson rules,⁵⁰⁻⁵² the B-site Co is FM coupled with both the A-site Mn and B'-site Re ions, and Mn and Re are AFM coupled. On account of the localized $3d$ orbit, the FM inter-site superexchange interaction between Mn and Co is supposed to play a role thus competes with the AFM intra-site couplings. It therefore explains that Co and Mn hold considerable canted spins whereas the spin of Re almost maintains the antiparallel alignment as listed in Table 1.

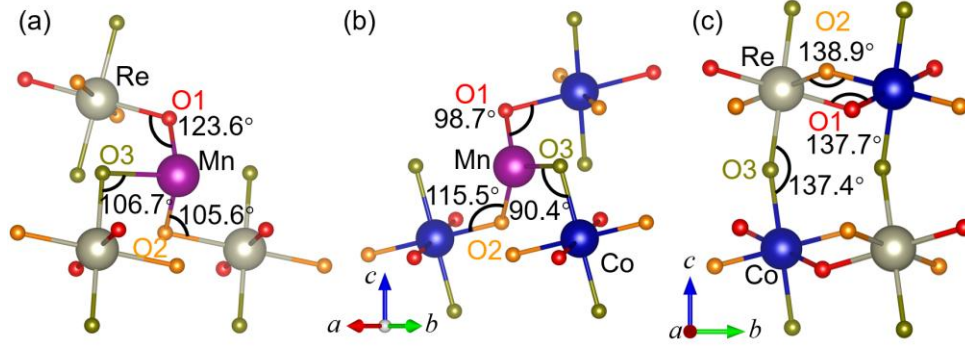


Figure 7. The bond angles of (a) Mn-O-Re, (b) Mn-O-Co and (c) Co-O-Re. The Mn, Co and Re ions are shown in purple, blue and grey, respectively. The different O sites are shown in red, orange and brown, respectively.

We further investigated the transport properties of MCRO. As shown in Figure 8a, the electrical resistivity increases with cooling, exceeding the measuring range ($10^6 \Omega \text{ cm}$) below 80 K, indicating either a semiconductive or an insulative behavior. The temperature dependent electrical resistivity can be well fitted with the thermal activation model within the temperature range 260–350 K with the formula $\rho = \rho_0 \times \exp(E_a/k_B T)$, where ρ_0 and E_a representing the residual resistance and the activation energy, respectively, and k_B is the Boltzmann constant. This demonstrates that MCRO is a semiconductor. The obtained energy gap from the fitting is $E_k = 2E_a = 0.29 \text{ eV}$, and the residual resistance is $0.11 \Omega \text{ cm}$.

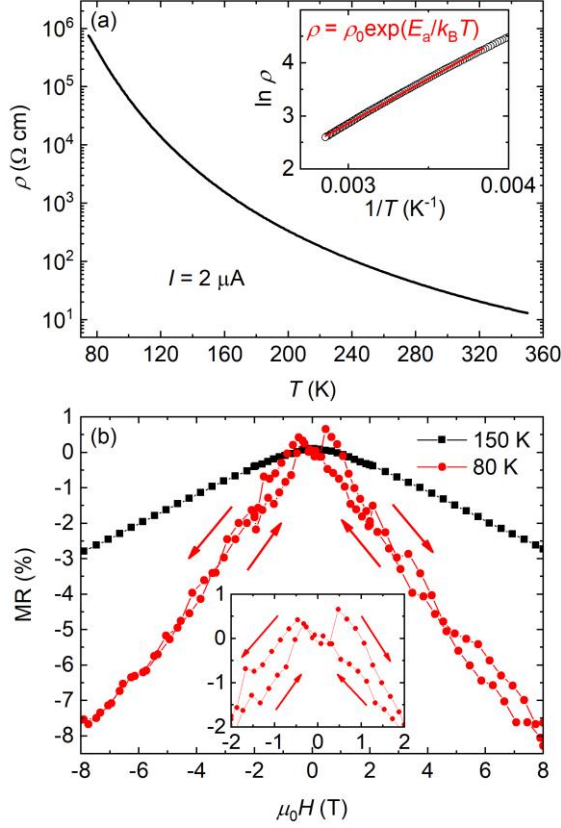


Figure 8. (a) Temperature dependent resistivity of MCRO. The inset displays the experimental data (black circles) and the thermal activation model fitting with formula $\rho = \rho_0 \times \exp(E_a/k_B T)$ in the temperature range 260–350 K. (b) Field dependent magnetoresistance of MCRO at 150 K and 80 K. The inset depicts the region of ± 2 T.

The canted AFM structure with a considerable net magnetic moment allow MCRO to be utilized as high-speed spin filtering by means of the TMR mechanism through magnetic domains and grain boundaries of polycrystalline MCRO.^{5,14} As displayed in Figure 8b, at 150 K ($> T_N$), the MR of MCRO is almost independent of the magnetic field, in agreement with a paramagnetic state. Note that the slight decrease of MR is caused by some extrinsic effects such as short-range magnetic correlations. On the other hand, at 80 K ($< T_N$), the MR increases to positive values under small magnetic field and then decreases to negative values upon further magnetic field increase, and is accompanied by a prominent coercivity. This butterfly-shaped MR is reminiscent of the spin-valve-type transport mechanism, which is in accordance with the tunnel effect between multi-layer junctions and/or grain boundaries.^{13,14,53,54} The MR reaches 8% at 80 K and 7 T, and depends linearly on the applied magnetic field above 2 T. Note that the electrical resistivity exceeds the

measuring range below 80 K. To take into consideration of the large coercivity at 2 K which can lead to a strong pinning effect of the spins,¹⁷ we thus speculate a much larger TMR at lower temperatures for a more conductive MCRO sample through disordering, doping, and/or oxygen vacancies.

Conclusions

In summary, the transition-metal-only double perovskite oxide $\text{Mn}_2\text{CoReO}_6$ was studied by element-selective x-ray absorption spectroscopy. The valence states of $\text{Mn}^{2+}/\text{Co}^{2+}/\text{Re}^{6+}$ were experimentally determined. An internal magnetic field against with the applied magnetic field was obtained, providing a microscopic insight of the intra-site antiferromagnetic couplings. Nevertheless, x-ray magnetic circular dichroic measurements manifest that all the Mn, Co and Re spins are canted and parallel with each other, and particularly, the 3d Mn and Co cations hold considerable canting moments, which can be ascribed to the competition between the intra- and inter-sites magnetic interactions. Moreover, a linear magnetoresistance effect was observed below T_N , which is resulted from the spin-valve-type tunneling through the grain boundaries. The concurrence of the antiferromagnetic nature as well as the linear magnetoresistance effect make $\text{Mn}_2\text{CoReO}_6$ a promising candidate for high-speed and energy-saving spintronics applications.

Supporting Information

Detailed lattice parameters, bond lengths and bond angles from SXRD refinement

Acknowledgements

This work was supported by the National Key R&D Program of China (Grant No. 2021YFA1400300), the National Natural Science Foundation of China (Grants No. 11934017, 12261131499, 11921004, 12304159, 12304268), the Beijing Natural Science Foundation (Grant No. Z2000007), and the Chinese Academy of Sciences (Grant No. XDB33000000). The synchrotron x-ray diffraction experiments were performed at SPring-8 with the approval of the Japan Synchrotron Radiation Research Institute (2023B1575). The authors thank DESY (Hamburg, Germany), a member of the Helmholtz Association HGF, for the provision of experimental facilities. Parts of this research were carried out at beamline P09 at PETRA III under proposal I-20200812. The 6T/2T/2T used for the XMCD measurements at P09 was funded in part by the

BMBF grant No. 05K2013 from the German Federal Ministry of Education and Research. The authors thank J. Linares Mardegan and Olaf Leupold for scientific and technical support at P09. Financial support for developing and building the PM2-VEKMAG beamline and VEKMAG end-station was provided by HZB and BMBF (Grant Nos. 05K10PC2, 05K10WR1, and 05K10KE1). The research in Dresden was partially supported by the DFG through SFB 1143. The authors acknowledge the support from the Max Planck-POSTECH-Hsinchu Center for Complex Phase Materials.

Notes

The authors declare no competing financial interest.

References

- 1 Fert, A. Nobel lecture: origin, development, and future of spintronics. *Rev. Mod. Phys.* **2008**, 80, 1517–1530.
- 2 Bibes, M.; Villegas, J. E.; Barthélémy, A. Ultrathin oxide films and interfaces for electronics and spintronics. *Adv. Phys.* **2011**, 60, 5–84.
- 3 Fusil, S.; Garcia, V.; Barthélémy, A.; Bibes, M. Magnetoelectric devices for spintronics. *Annu. Rev. Mater. Res.* **2014**, 44, 91–116.
- 4 Baibich, M. N.; Broto, J. M.; Fert, A.; Nguyen Van Dau, F.; Petroff, F.; Etienne, P.; Creuzet, G.; Friederich, A.; Chazelas, J. Giant magnetoresistance of (001)Fe/(001)Cr magnetic superlattices. *Phys. Rev. Lett.* **1988**, 61, 2472–2475.
- 5 Moodera, J. S.; Kinder, L. R.; Wong, T. M.; Meservey, R. Large magnetoresistance at room temperature in ferromagnetic thin film tunnel junctions. *Phys. Rev. Lett.* **1995**, 74, 3273–3276.
- 6 Bhatti, S.; Sbiaa, R.; Hirohata, A.; Ohno, H.; Fukami, S.; Piramanayagam, S. N. Spintronics based random access memory: a review. *Mater. Today* **2017**, 20, 530–548.
- 7 Kampfrath, T.; Sell, A.; Klatt, G.; Pashkin, A.; Mährlein, S.; Dekorsy, T.; Wolf, M.; Fiebig, M.; Leitenstorfer, A.; Huber, R. Coherent terahertz control of antiferromagnetic spin waves. *Nat. Photon.* **2011**, 5, 31–34.
- 8 Qin, P.; Yan, H.; Wang, X.; Chen, H.; Meng, Z.; Dong, J.; Zhu, M.; Cai, J.; Feng, Z.; Zhou, X.; et al. Room-temperature magnetoresistance in an all-antiferromagnetic tunnel junction. *Nature* **2023**, 613, 485–489.

- 9 Wang, X.; Chai, Y.; Zhou, L.; Cao, H.; Cruz, C.; Yang, J.; Dai, J.; Yin, Y.; Yuan, Z.; Zhang, S.; et al. Observation of magnetoelectric multiferroicity in a cubic perovskite system: $\text{LaMn}_3\text{Cr}_4\text{O}_{12}$. *Phys. Rev. Lett.* **2015**, 115, 087601.
- 10 Nakatsuji, S.; Kiyohara, N.; Higo, T. Large anomalous Hall effect in a non-collinear antiferromagnet at room temperature. *Nature* **2015**, 527, 212–215.
- 11 Železný, J.; Wadley, P.; Olejník, K.; Hoffmann, A.; Ohno, H. Spin transport and spin torque in antiferromagnetic devices. *Nat. Phys.* **2018**, 14, 220–228.
- 12 Němec, P.; Fiebig, M.; Kampfrath, T.; Kimel, A. V. Antiferromagnetic opto-spintronics. *Nat. Phys.* **2018**, 14, 229–241.
- 13 Kobayashi, K.-I.; Kimura, T.; Sawada, H.; Terakura, K.; Tokura, Y. Room-temperature magnetoresistance in an oxide material with an ordered double-perovskite structure. *Nature* **1998**, 395, 677–680.
- 14 Sarma, D. D.; Ray, S.; Tanaka, K.; Kobayashi, M.; Fujimori, A.; Sanyal, P.; Krishnamurthy, H. R.; Dasgupta, C. Intergranular magnetoresistance in $\text{Sr}_2\text{FeMoO}_6$ from a magnetic tunnel barrier mechanism across grain boundaries. *Phys. Rev. Lett.* **2007**, 98, 157205.
- 15 Kobayashi, K.-I.; Kimura, T.; Tomioka, Y.; Sawada, H.; Terakura, K. Intergrain tunneling magnetoresistance in polycrystals of the ordered double perovskite $\text{Sr}_2\text{FeReO}_6$. *Phys. Rev. B* **1999**, 59, 11159–11162.
- 16 Chen, J.; Wang, X.; Hu, Z.; Tjeng, L. H.; Agrestini, S.; Valvidares, M.; Chen, K.; Nataf, L.; Baudelet, F.; Nagao, M.; et al. Enhanced magnetization of the highest- T_C ferrimagnetic oxide $\text{Sr}_2\text{CrOsO}_6$. *Phys. Rev. B* **2020**, 102, 184418.
- 17 Deng, Z.; Wang, X.; Wang, M.; Shen, F.; Zhang, J.; Chen, Y.; Feng, H. L.; Xu, J.; Peng, Y.; Li, W.; et al. Giant exchange-bias-like effect at low cooling fields induced by pinned magnetic domains in Y_2NiIrO_6 double perovskite. *Adv. Mater.* **2023**, 35, 2209759.
- 18 Li, M.-R.; Retuerto, M.; Deng, Z.; Stephens, P. W.; Croft, M.; Huang, Q.; Wu, H.; Deng, X.; Kotliar, G.; Sánchez-Benítez, J.; et al. Giant magnetoresistance in the half-metallic double-perovskite ferrimagnet $\text{Mn}_2\text{FeReO}_6$. *Angew. Chem. Int. Ed.* **2015**, 54, 12069–12073.
- 19 Arévalo-López, A. M.; McNally, G. M.; Attfield, J. P. Large magnetization and frustration switching of magnetoresistance in the double-perovskite ferrimagnet $\text{Mn}_2\text{FeReO}_6$. *Angew. Chem. Int. Ed.* **2015**, 54, 12074–12077.
- 20 Akizuki, Y.; Yamada, I.; Fujita, K.; Taga, K.; Kawakami, T.; Mizumaki, M.; Tanaka, K.

- Rattling in the quadruple perovskite $\text{CuCu}_3\text{V}_4\text{O}_{12}$. *Angew. Chem. Int. Ed.* **2015**, 54, 10870–10874.
- 21 Li, M.-R.; McCabe, E. E.; Stephens, P. W.; Croft, M.; Collins, L.; Kalinin, S. V.; Deng, Z.; Retuerto, M.; Gupta, A. S.; Padmanabhan, H.; et al. Magnetorestriction-polarization coupling in multiferroic Mn_2MnWO_6 . *Nat. Commun.* **2017**, 8, 2037.
 - 22 Li, M.-R.; Hodges, J. P.; Retuerto, M.; Deng, Z.; Stephens, P. W.; Croft, M. C.; Deng, X.; Kotliar, G.; Sánchez-Benítez, J.; Walker, D.; et al. $\text{Mn}_2\text{MnReO}_6$: Synthesis and magnetic structure determination of a new transition-metal-only double perovskite canted antiferromagnet. *Chem. Mater.* **2016**, 28, 3148–3158.
 - 23 Frank, C. E.; McCabe, E. E.; Orlandi, F.; Manuel, P.; Tan, X.; Deng, Z.; Croft, M.; Cascos, V.; Emge, T.; Feng, H. L.; et al. $\text{Mn}_2\text{CoReO}_6$: a robust multisublattice antiferromagnetic perovskite with small A-site cations. *Chem. Commun.* **2019**, 55, 3331–3334.
 - 24 Larson, C.; Von Dreele, R. B. General structure analysis system (GSAS), Report No. LAUR 86-748 (Los Alamos National Laboratory, Los Alamos, NM, **1994**).
 - 25 Noll, T.; Radu, F. The mechanics of the VEKMAG experiment. Proceedings of the 9th mechanical engineering design of synchrotron radiation equipment and instrumentation conference (MEDSI2016), Barcelona, Spain, **2016** (JACoW, Geneva, 2017), 370–373.
 - 26 Retuerto, M.; García-Hernández, M.; Martínez-Lope, M. J.; Fernández-Díaz, M. T.; Attfield, J. P.; Alonso, J. A. Switching from ferro- to antiferromagnetism in A_2CrSbO_6 ($\text{A} = \text{Ca}, \text{Sr}$) double perovskites: a neutron diffraction study. *J. Mater. Chem.* **2007**, 17, 3555–3561.
 - 27 Brown, I. D.; Altermatt, D. Bond-valence parameters obtained from a systematic analysis of the inorganic crystal structure database. *Acta Crystallogr.* **1985**, B41, 244–247.
 - 28 Wiebe, C. R.; Greedan, J. E.; Kyriakou, P. P.; Luke, G. M.; Gardner, J. S.; Fukaya, A.; Gat-Malureanu, I. M.; Russo, P. L.; Savici, A. T.; Uemura, Y. J. Frustration-driven spin freezing in the $S = 1/2$ fcc perovskite $\text{Sr}_2\text{MgReO}_6$. *Phys. Rev. B* **2003**, 68, 134410.
 - 29 Burnus, T.; Hu, Z.; Wu, H.; Cezar, J. C.; Niitaka, S.; Takagi, H.; Chang, C.-F.; Brookes, N. B.; Lin, H.-J.; Jang, L.-Y.; et al. X-ray absorption and x-ray magnetic dichroism study on $\text{Ca}_3\text{CoRhO}_6$ and $\text{Ca}_3\text{FeRhO}_6$. *Phys. Rev. B* **2008**, 77, 205111.
 - 30 Chen, J.-M.; Chin, Y.-Y.; Valldor, M.; Hu, Z.; Lee, J.-M.; Haw, S.-C.; Hiraoka, N.; Ishii, H.; Pao, C.-W.; Tsuei, K.-D.; et al. A complete high-to-low spin state transition of trivalent cobalt ion in octahedral symmetry in $\text{SrCo}_{0.5}\text{Ru}_{0.5}\text{O}_{3-\delta}$. *J. Am. Chem. Soc.* **2014**, 136, 1514–1519.

- 31 Hu, Z.; Golden, M. S.; Fink, J.; Kaindl, G.; Warda, S. A.; Reinen, D.; Mahadevan, P.; Sarma, D. D. Hole distribution between the Ni 3d and O 2p orbitals in $\text{Nd}_{2-x}\text{Sr}_x\text{NiO}_{4-\delta}$. *Phys. Rev. B* **2000**, 61, 3739–3744.
- 32 Liu, Z.; Wang, X.; Ye, X.; Shen, X.; Bian, Y.; Ding, W.; Agrestini, S.; Liao, S.-C.; Lin, H.-J.; Chen, C.-T.; et al. Observation of A-site antiferromagnetic and B-site ferrimagnetic orderings in the quadruple perovskite oxide $\text{CaCu}_3\text{Co}_2\text{Re}_2\text{O}_{12}$. *Phys. Rev. B* **2021**, 103, 014414.
- 33 Long, Y.; Saito, T.; Mizumaki, M.; Agui, A.; Shimakawa, Y. Various valence states of square-coordinated Mn in A-site-ordered perovskites. *J. Am. Chem. Soc.* **2009**, 131, 16244–16247.
- 34 Agrestini, S.; Chen, K.; Kuo, C.-Y.; Zhao, L.; Lin, H.-J.; Chen, C.-T.; Rogalev, A.; Ohresser, P.; Chan, T.-S.; Weng, S.-C.; et al. Nature of the magnetism of iridium in the double perovskite $\text{Sr}_2\text{CoIrO}_6$. *Phys. Rev. B* **2019**, 100, 014443.
- 35 Feng, H. L.; Chen, J.; Hu, Z.; Wang, X.; Reehuis, M.; Adler, P.; Hoser, A.; Wu, M.-X.; Agrestini, S.; Vasili, H. B.; et al. From antiferromagnetism to high- T_C weak ferromagnetism manipulated by atomic rearrangement in $\text{Ba}_3\text{NiOs}_2\text{O}_9$. *Phys. Rev. Mater.* **2020** 4, 064420.
- 36 Thole, B. T.; Carra, P.; Sette, F.; van der Laan, G. X-ray circular dichroism as a probe of orbital magnetization. *Phys. Rev. Lett.* **1992**, 68, 1943–1946.
- 37 Carra, P.; Thole, B. T.; Altarelli, M.; Wang, X. X-ray circular dichroism and local magnetic fields. *Phys. Rev. Lett.* **1993**, 70, 694–697.
- 38 Saha-Dasgupta, T. Double perovskites with 3d and 4d/5d transition metals: compounds with promise. *Mater. Res. Express* **2020**, 7, 014003.
- 39 Chen, W.-t.; Mizumaki, M.; Seki, H.; Senn, M. S.; Saito, T.; Kan, D.; Attifield J. P.; Shimakawa, Y. A half-metallic A- and B-site-ordered quadruple perovskite oxide $\text{CaCu}_3\text{Fe}_2\text{Re}_2\text{O}_{12}$ with large magnetization and a high transition temperature. *Nat. Commun.* **2014**, 5, 3909.
- 40 Deng, H.; Liu, M.; Dai, J.; Hu, Z.; Kuo, C.; Yin, Y.; Yang, J.; Wang, X.; Zhao, Q.; Xu, Y.; et al. Strong enhancement of spin ordering by A-site magnetic ions in the ferrimagnet $\text{CaCu}_3\text{Fe}_2\text{Os}_2\text{O}_{12}$. *Phys. Rev. B* **2016**, 94, 024414.
- 41 Wang, X.; Liu, Z.; Deng, H.; Agrestini, S.; Chen, K.; Lee, J.-F.; Lin, H.-J.; Chen, C.-T.; Choueikani, F.; Ohresser, P.; et al. Comparative study on the magnetic and transport properties of B-site ordered and disordered $\text{CaCu}_3\text{Fe}_2\text{Os}_2\text{O}_{12}$. *Inorg. Chem.* **2022**, 61, 16929–16935.
- 42 Wang, X.; Hu, Z.; Agrestini, S.; Herrero-Martín, J.; Valvidares, M.; Sankar, R.; Chou, F.-C.;

- Chu, Y.-H.; Tanaka, A.; Tjeng, L. H. Evidence for largest room temperature magnetic signal from Co^{2+} in antiphase-free & fully inverted CoFe_2O_4 in multiferroic-ferrimagnetic BiFeO_3 - CoFe_2O_4 nanopillar thin films. *J. Magn. Magn. Mater.* **2021**, 530, 167940.
- 43 Liu, Z.; Zhang, S.; Wang, X.; Ye, X.; Qin, S.; Shen, X.; Lu, D.; Dai, J.; Cao, Y.; Chen, K.; et al. Realization of a half metal with a record-high Curie temperature in perovskite oxides. *Adv. Mater.* **2022**, 34, 2200626.
- 44 Tanaka, A.; Jo, T.; Resonant $3d$, $3p$ and $3s$ photoemission in transition metal oxides predicted at $2p$ threshold. *J. Phys. Soc. Jpn.* **1994**, 63, 2788–2807.
- 45 Sahu, R. K.; Hu, Z.; Rao, M. L.; Manoharan, S. S.; Schmidt, T.; Richter, B.; Knupfer, M.; Golden, M.; Fink, J.; Schneider, C. M. X-ray absorption spectra at the Ru and Mn $L_{2,3}$ edges and long-range ferromagnetism in $\text{SrRu}_{1-x}\text{Mn}_x\text{O}_3$ solid solutions ($0 \leq x \leq 0.5$). *Phys. Rev. B* **2002**, 66, 144415.
- 46 Burnus, T.; Hu, Z.; Haverkort, M. W.; Cezar, J. C.; Flahaut, D.; Hardy, V.; Maignan, A.; Brookes, N. B.; Tanaka, A.; Hsieh, H. H.; et al. Valence, spin, and orbital state of Co ions in one-dimensional $\text{Ca}_3\text{Co}_2\text{O}_6$: An x-ray absorption and magnetic circular dichroism study, *Phys. Rev. B* **2006**, 74, 245111.
- 47 Parameters used in cluster calculations (eV). For Mn^{2+} : $U_{dd} = 7.0$, $U_{cd} = 8.0$, $\Delta = 6.5$, $H_{\text{ex}} = -8.52 \times 10^{-4}$. Considering the low symmetry of the MnO_8 polyhedron, the crystal field was obtained from the Madelung potential and the hybridization was obtained from Harrison's prescription. For Co^{2+} (O_h): $U_{dd} = 6.5$, $U_{cd} = 8.2$, $\Delta = 6.5$, $10Dq = 0.45$, $V(e_g) = 1.92$, $V(t_{2g}) = 1.02$, $H_{\text{ex}} = -8.30 \times 10^{-4}$. For Re^{6+} (O_h): $U_{dd} = 1.0$, $U_{cd} = 3.0$, $\Delta = -2.0$, $10Dq = 4.6$, $V(e_g) = 3.81$, $V(t_{2g}) = 2.03$, $H_{\text{ex}} = -5.80 \times 10^{-5}$. Slater integrals were set to 90%, 80% and 70% of Hartree-Fock values for Mn^{2+} , Co^{2+} and Re^{6+} , respectively.
- 48 Morrow, R.; Mishra, R.; Restrepo, O. D.; Ball, M. R.; Windl, W.; Wurmehl, S.; Stockert, U.; Büchner, B.; Woodward, P. M. Independent ordering of two interpenetrating magnetic sublattices in the double perovskite $\text{Sr}_2\text{CoOsO}_6$. *J. Am. Chem. Soc.* **2013**, 135, 18824–18830.
- 49 Toyoda, M.; Yamauchi, K.; Oguchi, T. Ab initio study of magnetic coupling in $\text{CaCu}_3\text{B}_4\text{O}_{12}$ (B = Ti, Ge, Zr, and Sn). *Phys. Rev. B* **2013**, 87, 224430.
- 50 Anderson, P. W. Antiferromagnetism. Theory of superexchange interaction. *Phys. Rev.* **1950**, 79, 350.
- 51 Goodenough, J. B. Theory of the role of covalence in the perovskite-type manganites [La,

- M*(II)]MnO₃. Phys. Rev. **1955**, 100, 564.
- 52 Kanamori, J. Superexchange interaction and symmetry properties of electron orbitals. J. Phys. Chem. Solids **1959**, 10, 87.
- 53 Guo, J.; Wang, S.; Li, W.; Lu, D.; Ye, X.; Liu, Z.; Qin, S.; Wang, X.; Hu, Z.; Lin, H.-J.; et al. A-site Mn²⁺ tuned magnetism and electrical transport properties in the transition-metal-only perovskite oxide MnCu₃Mn₄O₁₂. Phys. Rev. B **2022**, 105, 054409.
- 54 Pradhan, K.; Sanyal, P.; Saha-Dasgupta, T. Magnetism in cation-ordered multicomponent oxide perovskites. Chem. Mater. **2024**, 36, 3829–3836.

TOC Graphic

